



Article

# Effect of Hofmeister Ions on Transport Properties of Aqueous Solutions of Sodium Hyaluronate

Lenka Musilová<sup>1,2</sup>, Aleš Mráček<sup>1,2,\*</sup> , Věra Kašpárková<sup>2,3</sup>, Antonín Minařík<sup>1,2</sup>, Artur J. M. Valente<sup>4,\*</sup>, Eduarda F. G. Azevedo<sup>4</sup>, Luis M. P. Veríssimo<sup>4</sup>, M. Melia Rodrigo<sup>4</sup>, Miguel A. Esteso<sup>5,6</sup> and Ana C. F. Ribeiro<sup>4</sup>

- <sup>1</sup> Department of Physics and Materials Engineering, Faculty of Technology, Tomas Bata University in Zlín, Vavrečkova 275, 760 01 Zlín, Czech Republic; lmusilova@utb.cz (L.M.); minarik@utb.cz (A.M.)
- <sup>2</sup> Centre of Polymer Systems, Tomas Bata University in Zlín, tř. Tomáše Bati 5678, 760 01 Zlín, Czech Republic; vkasparkova@utb.cz
- <sup>3</sup> Department of Fat, Surfactant and Cosmetics Technology, Faculty of Technology, Tomas Bata University in Zlín, Vavrečkova 275, 762 72 Zlín, Czech Republic
- <sup>4</sup> Department of Chemistry, University of Coimbra, CQC, 3004-535 Coimbra, Portugal; edy.gil.azevedo@gmail.com (E.F.G.A.); verissimo@uc.pt (L.M.P.V.); mmelia.rodrigo@uah.es (M.M.R.); anacfrb@ci.uc.pt (A.C.F.R.)
- <sup>5</sup> U.D. Química Física, Universidad de Alcalá, 28871 Alcalá de Henares, Spain; mangel.esteso@ucavila.es
- <sup>6</sup> Universidad Católica Santa Teresa de Jesús de Ávila, Calle los Canteros s/n, 05005 Ávila, Spain
- \* Correspondence: mracek@utb.cz (A.M.); avalente@ci.uc.pt (A.J.M.V.);  
Tel.: +420-608-707-577 (A.M.); +351-239-854-459 (A.J.M.V.)



**Citation:** Musilová, L.; Mráček, A.; Kašpárková, V.; Minařík, A.; Valente, A.J.M.; Azevedo, E.F.G.; Veríssimo, L.M.P.; Rodrigo, M.M.; Esteso, M.A.; Ribeiro, A.C.F. Effect of Hofmeister Ions on Transport Properties of Aqueous Solutions of Sodium Hyaluronate. *Int. J. Mol. Sci.* **2021**, *22*, 1932. <https://doi.org/10.3390/ijms22041932>

Academic Editor:

Alexander B. Doktorov

Received: 24 January 2021

Accepted: 11 February 2021

Published: 16 February 2021

**Publisher's Note:** MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.




**Copyright:** © 2021 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

**Abstract:** Tracer diffusion coefficients obtained from the Taylor dispersion technique at 25.0 °C were measured to study the influence of sodium, ammonium and magnesium salts at 0.01 and 0.1 mol dm<sup>-3</sup> on the transport behavior of sodium hyaluronate (NaHy, 0.1%). The selection of these salts was based on their position in Hofmeister series, which describe the specific influence of different ions (cations and anions) on some physicochemical properties of a system that can be interpreted as a salting-in or salting-out effect. In our case, in general, an increase in the ionic strength (i.e., concentrations at 0.01 mol dm<sup>-3</sup>) led to a significant decrease in the limiting diffusion coefficient of the NaHy 0.1%, indicating, in those circumstances, the presence of salting-in effects. However, the opposite effect (salting-out) was verified with the increase in concentration of some salts, mainly for NH<sub>4</sub>SCN at 0.1 mol dm<sup>-3</sup>. In this particular salt, the cation is weakly hydrated and, consequently, its presence does not favor interactions between NaHy and water molecules, promoting, in those circumstances, less resistance to the movement of NaHy and thus to the increase of its diffusion (19%). These data, complemented by viscosity measurements, permit us to have a better understanding about the effect of these salts on the transport behaviour of NaHy.

**Keywords:** sodium hyaluronate; transport properties; viscosity; Hofmeister series

## 1. Introduction


Hyaluronan (sodium salt of hyaluronic acid, NaHy), was firstly obtained by Meyer et al. [1] from the vitreous humor of cattle eyes. It consists of a disaccharide repeating sequence of D-glucuronic acid and N-acetyl-D-glucosamine, linked via alternating  $\beta$ -(1→4) and  $\beta$ -(1→3) glycosidic bonds (Figure 1) [2]. Hyaluronic acid (HyA) is a natural linear polysaccharide, being naturally present and abundant in all biologic fluids of some bacteria and all vertebrates [2–4]. Due to its biocompatibility, biodegradability and presence in the native extracellular matrix of tissues [5], HyA has been extensively applied for medical [6,7] and biomedical applications [8,9], including drug delivery [10–12], bioprinting [13] and tissue engineering [14], cosmetics [15] and wastewater treatment [16].

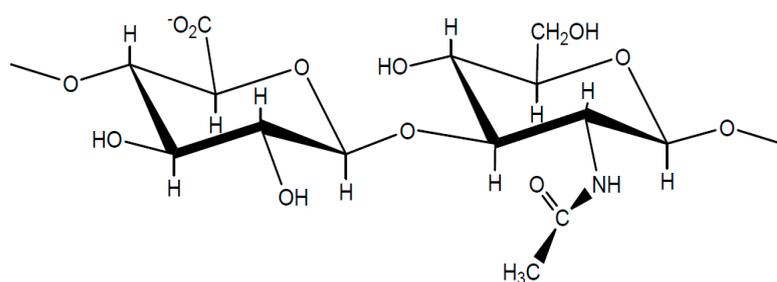

**Figure 1.** Molecular structure of the disaccharide repeating unit in hyaluronic acid salt.

For most of these applications, knowledge of the transport properties of HyA in aqueous solutions plays a key role. For example, whilst for electrospinning the solution viscosity is relevant, for drug delivery the understanding of mass transport by diffusion is essential as a limiting kinetic constant. Despite this, only few articles describe the behaviour of hyaluronic acid solutions in terms of transport properties. Verissimo et al. [17] reported mutual diffusion coefficients of sodium hyaluronate in the concentration range  $0.50$  to  $50 \text{ g dm}^{-3}$ , at  $25 \text{ }^\circ\text{C}$ , allowing the estimation of different parameters such as the diffusion coefficient at infinitesimal concentration, the limiting ionic conductivity and the tracer diffusion coefficient of hyaluronate ion. Later, these studies were complemented by viscosity data, and its influence on the diffusion coefficients were discussed [18]. However, only few data have shown the effect of the ionic strength on the HyA behavior in aqueous solution. By using optical techniques, Wik and Comper studied the effect of the ionic strength on the mutual diffusion coefficient of hyaluronate. However, the obtained results must be considered as approximate according to the authors [19]. Some of us [20] have reported dynamic light-scattering (DLS), viscosity and surface tension (SFT) measurements to characterize the influence of the following salts:  $\text{Na}_2\text{SO}_4$ ,  $(\text{NH}_4)_2\text{SO}_4$ ,  $\text{NaSCN}$ ,  $\text{NH}_4\text{SCN}$  and  $\text{NaCl}$ , on the behavior of hyaluronan in diluted solutions at a temperature range of  $15$ – $45 \text{ }^\circ\text{C}$ . In the sequence of this work, we intend to extend these studies measuring viscosities for the same aqueous systems but using other NaHy with lower molecular mass ( $M_w = 124 \text{ kDa}$ ), and also characterise the influence of these particular salts on the diffusion of NaHy using the same samples of this compound (i.e.,  $M_w = 1.8$ – $2.1 \text{ MDa}$  and  $M_w = 124 \text{ kDa}$ ). The selection of these salts was based on the ordering of Hofmeister series [21] and its related properties (viscosity or surface energy and entropies of ion solvation) [22], this classification being proposed in accordance with the abilities of these ions to induce the water structuring or breaking (Figure 2). The ions on the left side are called kosmotropes (“water structure makers”), while on the right side are chaotropes (“water structure breakers”) [21]. It is known that Hofmeister or specific ion effects affect some physicochemical properties of aqueous [23,24] and nonaqueous [25,26] systems. As an example, there are studies made by Mráček et al. [27] about the influence of Hofmeister series ions on HyA behaviour and HyA film-swelling. Additionally diffusion coefficients of water on the swelling process of films of sodium hyaluronate and their hydrophobically modified derivatives have also been studied [28,29]. Mráček et al. [29] also showed, by using viscosity measurements, that the presence of specific ions such as sulphate and thiocyanate anions, affects the behaviour of NaHy in aqueous solutions due to its ability to act as “structure making” and “structure breaking”, leading to the expansion or contraction of the NaHy coil.

Thus, the present work focuses on the investigation of the effect of different salts ( $\text{Na}_2\text{SO}_4$ ,  $(\text{NH}_4)_2\text{SO}_4$ ,  $\text{MgSO}_4$ ,  $\text{NaSCN}$ ,  $\text{NH}_4\text{SCN}$ ,  $\text{NaCl}$  and  $\text{LiCl}$ ), with different kosmotropic/chaotropic [30,31], on the mutual interdiffusion coefficients and viscosities of NaHy, at  $25 \text{ }^\circ\text{C}$ .

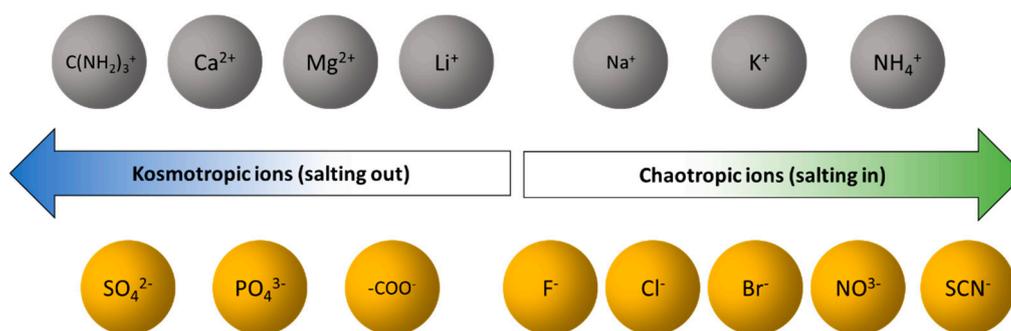

**Figure 2.** Typical ordering of Hofmeister ions series based on precipitation studies of solutions of typical and anionic proteins.

## 2. Results and Discussion

### 2.1. Apparent Tracer Diffusion Coefficients of Sodium Hyaluronate

Tables 1 and 2 present the apparent tracer experimental diffusion coefficients,  ${}^{\text{app}}D_{\text{IT}}^0$ , for aqueous pseudo binary systems containing hyaluronate ( $M_w = 1.8\text{--}2.1$  MDa and  $M_w = 124$  kDa) and some salts at  $0.01$  or  $0.1$  mol  $\text{dm}^{-3}$  at  $25$  °C. These  ${}^{\text{app}}D_{\text{IT}}^0$  values were obtained from at least three independent runs. The uncertainty of these values is not greater than 3%.

**Table 1.** Tracer diffusion coefficients,  ${}^{\text{app}}D_{\text{IT}}^0$ , for sodium hyaluronate (NaHy) 0.1% ( $M_w = 1.8$  MDa) (component 1) in aqueous solutions containing different salts (component 2) at  $0.01$  mol  $\text{dm}^{-3}$  and  $0.1$  mol  $\text{dm}^{-3}$ , and the respective standard deviations of the mean  ${}^1$ ,  $S_D$ , and at  $25$  °C.

	Cation ( $K_C$ or $CH_C$ ) <sup>2</sup>	Anion ( $K_A$ or $CH_A$ ) <sup>2</sup>	${}^{\text{app}}D_{\text{IT}}^0 \pm S_D / (10^{-9} \text{m}^2 \text{s}^{-1})$ ( $0.01$ mol $\text{dm}^{-3}$ )	$(\Delta {}^{\text{app}}D_{\text{IT}}^0 / D^0)$ % <sup>3</sup>	${}^{\text{app}}D_{\text{IT}}^0 \pm S_D / (10^{-9} \text{m}^2 \text{s}^{-1})$ ( $0.1$ mol $\text{dm}^{-3}$ )	$(\Delta {}^{\text{app}}D_{\text{IT}}^0 / D^0)$ % <sup>3</sup>
MgSO <sub>4</sub>	(Mg <sup>2+</sup> , K <sub>C</sub> )	(SO <sub>4</sub> <sup>2-</sup> , K <sub>A</sub> )	$0.609 \pm 0.004$	-54.3	$0.715 \pm 0.005$	-46.4
NaSCN	(Na <sup>+</sup> , K <sub>C</sub> )	(SCN <sup>-</sup> , CH <sub>A</sub> )	$0.858 \pm 0.004$	-35.6	$1.421 \pm 0.004$	6.6
Na <sub>2</sub> SO <sub>4</sub>	(Na <sup>+</sup> , K <sub>C</sub> )	(SO <sub>4</sub> <sup>2-</sup> , K <sub>A</sub> )	$0.860 \pm 0.019$	-35.5	$1.016 \pm 0.003$	-23.8
NH <sub>4</sub> SCN	(NH <sub>4</sub> <sup>+</sup> , CH <sub>C</sub> )	(SCN <sup>-</sup> , CH <sub>A</sub> )	$1.080 \pm 0.020$	-18.9	$1.595 \pm 0.007$	19.7
NaCl	(Na <sup>+</sup> , K <sub>C</sub> )	(Cl <sup>-</sup> , CH <sub>A</sub> )	$1.090 \pm 0.020$	-25.7	$1.435 \pm 0.008$	7.6
LiCl	(Li <sup>+</sup> , K <sub>C</sub> )	(Cl <sup>-</sup> , CH <sub>A</sub> )	$1.360 \pm 0.003$	2.0	$1.351 \pm 0.005$	1.3
(NH <sub>4</sub> ) <sub>2</sub> SO <sub>4</sub>	(NH <sub>4</sub> <sup>+</sup> , CH <sub>C</sub> )	(SO <sub>4</sub> <sup>2-</sup> , K <sub>A</sub> )	$1.109 \pm 0.008$	-16.8	$1.313 \pm 0.004$	-1.5

<sup>1</sup> Averaged result for  $n = 3$  experiments. Standard uncertainties  $u$  are:  $u_r(c) = 0.03$ ;  $u(T) = 0.01$  °C and  $u(P) = 2.03$  kPa. <sup>2</sup>  $K_C$  or  $CH_C$ , and  $K_A$  or  $CH_A$ , means kosmotropic cation (or chaotropic cation), and kosmotropic anion (or chaotropic anion). <sup>3</sup>  $(\Delta {}^{\text{app}}D_{\text{IT}}^0 / D^0)$  represents the deviations between the apparent tracer diffusion coefficients of NaHy in aqueous electrolytic solutions at  $0.01$  or  $0.1$  mol  $\text{dm}^{-3}$ , and the limiting diffusion coefficients of the aqueous solutions of NaHy at the same temperature  $D^0 = 1.333 \times 10^{-9} \text{m}^2 \text{s}^{-1}$  [18].

**Table 2.** Tracer diffusion coefficients,  ${}^{\text{app}}D_{\text{IT}}^0$ , for NaHy 0.1% ( $M_w = 124$  kDa) (component 1) in aqueous solutions containing different salts (component 2) at  $0.01$  mol  $\text{dm}^{-3}$  and  $0.1$  mol  $\text{dm}^{-3}$ , and the respective standard deviations of the mean  ${}^1$ ,  $S_D$ , and at  $25$  °C.

	Cation ( $K_C$ or $CH_C$ ) <sup>2</sup>	Anion ( $K_A$ or $CH_A$ ) <sup>2</sup>	${}^{\text{app}}D_{\text{IT}}^0 \pm S_D / (10^{-9} \text{m}^2 \text{s}^{-1})$ ( $0.01$ mol $\text{dm}^{-3}$ )	$(\Delta {}^{\text{app}}D_{\text{IT}}^0 / D^0)$ % <sup>3</sup>	${}^{\text{app}}D_{\text{IT}}^0 \pm S_D / (10^{-9} \text{m}^2 \text{s}^{-1})$ ( $0.1$ mol $\text{dm}^{-3}$ )	$(\Delta {}^{\text{app}}D_{\text{IT}}^0 / D^0)$ % <sup>3</sup>
MgSO <sub>4</sub>	(Mg <sup>2+</sup> , K <sub>C</sub> )	(SO <sub>4</sub> <sup>2-</sup> , K <sub>A</sub> )	$0.709 \pm 0.002$	-31.6	$0.754 \pm 0.005$	-27.2
NaSCN	(Na <sup>+</sup> , K <sub>C</sub> )	(SCN <sup>-</sup> , CH <sub>A</sub> )	$1.136 \pm 0.002$	9.6	$1.325 \pm 0.010$	27.8
Na <sub>2</sub> SO <sub>4</sub>	(Na <sup>+</sup> , K <sub>C</sub> )	(SO <sub>4</sub> <sup>2-</sup> , K <sub>A</sub> )	$0.868 \pm 0.010$	-16.2	$1.075 \pm 0.020$	3.8
NH <sub>4</sub> SCN	(NH <sub>4</sub> <sup>+</sup> , CH <sub>C</sub> )	(SCN <sup>-</sup> , CH <sub>A</sub> )	$1.380 \pm 0.010$	33.2	$1.563 \pm 0.001$	50.9
NaCl	(Na <sup>+</sup> , K <sub>C</sub> )	(Cl <sup>-</sup> , CH <sub>A</sub> )	$0.947 \pm 0.002$	-8.6	$1.426 \pm 0.005$	37.6
LiCl	(Li <sup>+</sup> , K <sub>C</sub> )	(Cl <sup>-</sup> , CH <sub>A</sub> )	$1.282 \pm 0.005$	23.4	$1.228 \pm 0.005$	18.5
(NH <sub>4</sub> ) <sub>2</sub> SO <sub>4</sub>	(NH <sub>4</sub> <sup>+</sup> , CH <sub>C</sub> )	(SO <sub>4</sub> <sup>2-</sup> , K <sub>A</sub> )	$1.200 \pm 0.005$	15.8	$1.490 \pm 0.004$	43.8

<sup>1</sup> Averaged result for  $n = 3$  experiments. Standard uncertainties  $u$  are:  $u_r(c) = 0.03$ ;  $u(T) = 0.01$  °C and  $u(P) = 2.03$  kPa. <sup>2</sup>  $K_C$  or  $CH_C$ , and  $K_A$  or  $CH_A$ , means kosmotropic cation (or chaotropic cation), and kosmotropic anion (or chaotropic anion). <sup>3</sup>  $(\Delta {}^{\text{app}}D_{\text{IT}}^0 / D^0)$  represents the deviations between the apparent tracer diffusion coefficients of NaHy in aqueous electrolytic solutions at  $0.01$  or  $0.1$  mol  $\text{dm}^{-3}$ , and the limiting diffusion coefficients of the aqueous solutions of NaHy at the same temperature  $D^0 = 1.036 \times 10^{-9} \text{m}^2 \text{s}^{-1}$  [18] obtained by extrapolated values obtained from the  $D$  least-squares for three injections of NaHy in water (that is, for  $c = 0.1, 0.5$  and  $1$  g  $\text{dm}^{-3}$ , we obtained  $D = 1.014, 0.859$  and  $0.724 \times 10^{-9} \text{m}^2 \text{s}^{-1}$ ).

From Table 1, it can be observed, in general, that almost all added salts at  $0.01$  mol  $\text{dm}^{-3}$  contributed to the decrease of the diffusion of NaHy ( $M_w = 1.8\text{--}2.1$  MDa). In fact, the devia-

tions between the tracer diffusion coefficient values of NaHy in these supporting electrolytes and the limiting diffusion coefficient of the NaHy in water, at the same temperature, are negative (i.e.,  ${}^{\text{app}}D_{1\text{T}}^0 < D_{\text{NaHy}}^0$ ). However, these deviations were more significant for systems containing salts at  $0.01 \text{ mol dm}^{-3}$ . In these cases, these negative deviations (at most,  $-54\%$  for  $\text{MgSO}_4$ ), indicate the presence of salting-in effects.

A possible explanation for this phenomenon can be given if we consider that the  $\text{Mg}^{2+}$  ions are classified as poorly hydrated kosmotropic cations (Figure 2, and thus promote the salting-in effect, contributing to the contraction of NaHy chain and inducing a significant increasing of its chain stiffness. In these circumstances, there is the possibility to have a folded structure involving intramolecular hydrogen bonds. Similar behaviour is also observed in salts containing thiocyanates at  $0.01 \text{ mol dm}^{-3}$ , as well as chlorides at same concentration.

Support for these facts is shown in previous viscosity studies for the same systems [20], that is, NaHy in water and in saline solutions. It was concluded that the absence of salts leads to the increase of the repulsions between the unities of sodium hyaluronate, and consequently to the increase of the hydrodynamic volume of the coil of NaHy and, of course, of its viscosity. However, at high ionic strength, the charges due to the carboxylate groups on the NaHy chain are completely screened, thus diminishing the repulsion between them, which hinders the expansion of the coil.

The entities of NaHy offer more frictional resistance to motion through the liquid and, consequently, the diffusion coefficient of this aqueous system becomes smaller.

Concerning the other sulphates,  $(\text{NH}_4)_2\text{SO}_4$ , and  $\text{Na}_2\text{SO}_4$ , we can verify the deviations are less accentuated (that is,  $-16.8\%$  and  $-35.5\%$ ). This is not a surprise if we take in account that  $\text{NH}_4^+$  (chaotropic) and  $\text{Na}^+$  (border line between chaotropic and kosmotropic) cations are considered hydrated.


However, some added salts at  $c = 0.1 \text{ mol dm}^{-3}$ , with special relevance for  $\text{NH}_4\text{SCN}$ , increased the value of the diffusion coefficient  ${}^{\text{app}}D_{1\text{T}}^0$  of the NaHy from 6 to 20% (this maximum value was observed with  $\text{NH}_4\text{SCN}$ , indicating the presence of salting-out effects.  $\text{NH}_4^+$  being a chaotropic cation, will favour interactions between NaHy and water, and, consequently, the entities of NaHy offer less frictional resistance to motion through the liquid. Thus, the diffusion coefficient of this aqueous system becomes larger.

Relative to the study of the effect of the same salts on diffusion of NaHy but having a lower molecular mass (Table 2), it was observed that, in general, the deviations between the apparent tracer diffusion coefficients of NaHy in aqueous electrolytic solutions at  $0.01$  or  $0.1 \text{ mol dm}^{-3}$ , and the limiting diffusion coefficient of the aqueous solutions of NaHy at the same temperature were positive. In those circumstances, we can say that NaHy with lower molecular mass has less unities of NaHy in water and, consequently, has less interactions between these entities and water molecules, thus, leading to the increased diffusion coefficient.

## 2.2. Viscosity

Viscosimetry is an efficient method suitable for determining changes in the conformation of polymers in solutions. Using this method, viscosity of diluted polymer solutions can be expressed by limiting viscosity number  $[\eta]$  commonly calculated according to the Huggins equation through extrapolation of reduced viscosity  $\eta_{\text{red}}$  versus concentration dependence to zero concentration. However, interesting information can be obtained about the behaviour of polymers from the course of the viscosity curves, mainly in the case when the studied polymer belongs to the polyelectrolyte group, which true for NaHy. Therefore, in this work, we evaluated viscosity data for NaHy with  $M_w = 124 \text{ kDa}$  from the following two points of view: (1) we compared values of  $\eta_{\text{red}}$  for NaHy in the aqueous salt solutions determined at the highest polymer concentration of  $1.5 \text{ g L}^{-1}$ ; and (2) we evaluated the course of the  $\eta_{\text{red}}$  versus  $c$  dependence. Here, it is mainly interesting to look into polymer behaviour at the lowest concentrations ( $0.1$  to  $0.5 \text{ g L}^{-1}$ ).

We assessed the values of reduced viscosity  $\eta_{red}$  at the concentration of  $1.5 \text{ g L}^{-1}$  in presence of studied salts and they decreased in the following order:  $\text{Na}_2\text{SO}_4 > (\text{NH}_4)_2\text{SO}_4 > \text{NaSCN} > \text{LiCl} > \text{NH}_4\text{SCN} > \text{NaCl} > \text{MgSO}_4$  (Figure 3). Looking at the order, it is seen that the behaviour of sulfates with monovalent cations  $\text{Na}^+$  or  $\text{NH}_4^+$  differs from sulfate with divalent  $\text{Mg}^{2+}$ , which obviously illustrates that the type of cation present in the solution affects the NaHy conformation. Indeed, in the presence of salts, part of the ionized groups on the polymer chain can be neutralized and the polymer can form the more compact conformation. This effect is controlled by the type of counterion in the solution, and the association of polymer coil diminishes in the order roughly following the Hofmeister series, with divalent cations being more efficient in comparison with monovalent ones causing bigger coil shrinkage [32]. However, influence of anions on coil expansion can also be noticed. At this highest polymer concentration, the  $\eta_{red}$  values are higher for NaHy in sulfates with monovalent cations ( $\text{Na}_2\text{SO}_4$ ,  $(\text{NH}_4)_2\text{SO}_4$ ) than  $\eta_{red}$  for NaHy in both thioisocyanates ( $\text{NaSCN}$ ,  $\text{NH}_4\text{SCN}$ ). This shows the smaller expansion of the NaHy coil in the presence of the  $\text{SCN}^-$ . Here, the described behaviour of NaHy conforms with findings reported in [20] for NaHy with notably higher molecular mass of 1.8–2.1 MDa.

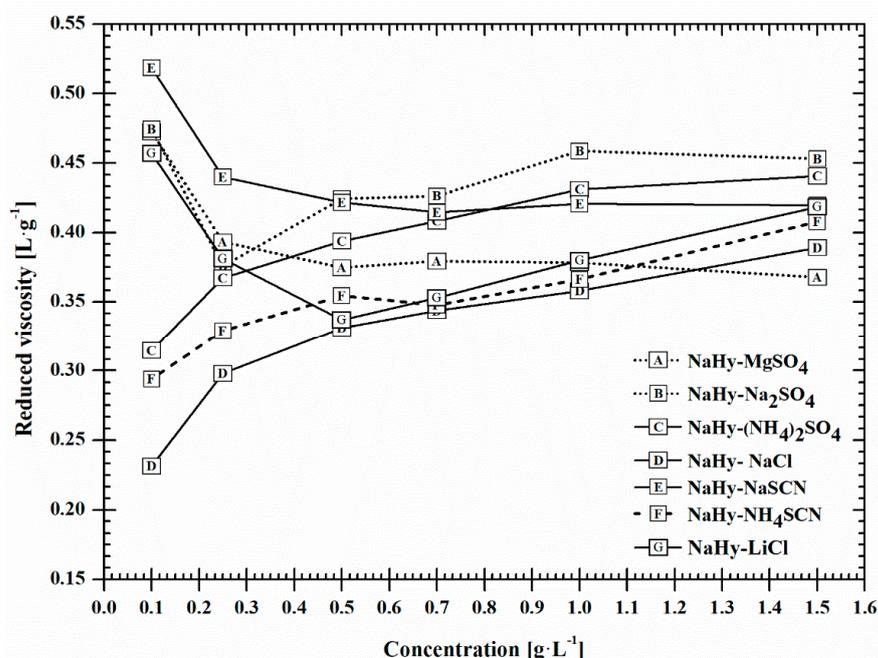

**Figure 3.** Dependence of reduced viscosity on concentration determined for NaHy dissolved in studied salts plotted according to Huggins.

The course of the  $\eta_{red}$  vs.  $c$  dependences depicted in Figure 3 affords additional interesting information on the studied samples and proves that NaHy behaves as typical polyelectrolyte polymer. This type of behaviour is commonly characterized by a nonlinear course of the  $\eta_{red}$  vs.  $c$  plot with upward curvature at the lowest NaHy concentrations, recorded mainly for NaHy dissolved in demineralised water (Figure 4).

If we look at Figure 3 in more detail, the  $\eta_{red}$  of all NaHy solutions decrease linearly with decreasing polymer concentration down to  $\approx 0.5 \text{ g L}^{-1}$  with a slope depending on the type of the dissolved salt. However, at the lowest concentrations  $0.25$  to  $0.1 \text{ g L}^{-1}$ , some of the salts ( $\text{NaSCN}$ ,  $\text{Na}_2\text{SO}_4$ ,  $\text{MgSO}_4$ ,  $\text{LiCl}$ ) induce the upwards curvature of the viscosity curve similar to NaHy in water. In contrast,  $\eta_{red}$  vs.  $c$  dependences for  $(\text{NH}_4)_2\text{SO}_4$ ,  $\text{NH}_4\text{SCN}$  and  $\text{NaCl}$  curve downwards. If we accept the prerequisite that the  $\text{NaCl}$  behaviour is exceptional due to the “borderline” position of both anion and cation in Hofmeister series, both these salts ( $(\text{NH}_4)_2\text{SO}_4$ ,  $\text{NH}_4\text{SCN}$ ) have it in common that a chaotropic cation is present. On the contrary, the upwards curvature can be observed for NaHy dissolved

in salts containing kosmotropic  $Mg^{2+}$  and  $Na^+$ , which is also classified among the kosmotropes, though it is positioned at the “borderline”. At these two lowest concentrations, the NaHy is highly diluted and the effect of dissolved salts begins to predominate over the effect of polymer. The polymer-polymer interactions are notably reduced relatively to polymer-solvent interactions, which prevail. This type of the salt, which can interact both with polymer and water molecules, starts to impact more on the polymer viscosity, which is also visible at the graph curves. At the lowest NaHy concentrations, the salts or more specifically their cations and anions, influence the structure of water in terms of “structure making” or “structure breaking”. In this respect it can be emphasized that chaotropic ions that disrupt the structure of bulk water favour polymer shrinkage as the entropic difference between bound water and bulk water increases [33].

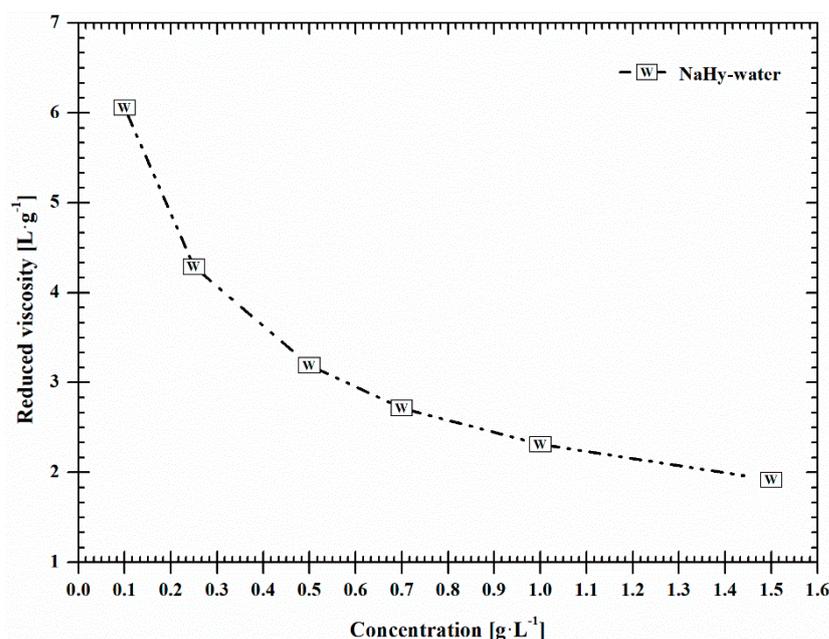


Figure 4. Reduced viscosity of NaHy in water.

In this respect, it is interesting to look into the viscosity of aqueous solutions of salts in the absence of the polymer. Here the viscosity increases in the following order  $NH_4SCN < H_2O < (NH_4)_2SO_4 < NaSCN < NaCl < Na_2SO_4 < LiCl < MgSO_4$ . Relatively to the viscosity of demineralized water, only  $NH_4SCN$  the salt with both chaotropic cation and anion ( $CH_3CH_2COO^-$ ), decreases the viscosity of water. In presence of all other tested salts, whether they are combination of  $CH_3COO^-$ ,  $K^+CH_2COO^-$  or  $K^+CH_2COO^-$ , the viscosity of water with salt increases relatively to that of demineralised water. According to Applebey [34], the effect of water dissolved ions on viscosity can be divided into two main effects: 1) decrease in viscosity caused by the breakdown of molecular clusters of water,  $(H_2O)_3$ , to simple molecules, and 2) increase in viscosity caused by the presence of salt ions and nonionized salt molecules. In the case of ions that are not fully hydrated, such as  $Cs^+$ ,  $K^+$ ,  $NH_4^+$ ,  $I^-$ ,  $Br^-$ ,  $NO_3^-$ , the decrease in viscosity is likely caused by the breakdown of clusters of water molecules. However, as most ions are fully hydrated, they are expected to increase the viscosity of water.

Table 3 compares the effect of the salts on the NaHy behaviour evaluated from diffusion coefficients and viscosity data. The values of apparent tracer diffusion coefficients  ${}^{app}D_{IT}^0$  of NaHy with  $M_w = 124$  kDa, determined in presence of salts with ionic strength  $0.1$  mol  $L^{-1}$  at  $25$  °C, are sorted by the increasing values corresponding with values of  $\eta_{red}$  determined for NaHy at the lowest and the highest polymer concentrations and viscosity of aqueous salt solutions in the absence of NaHy. Here, it is obvious that the two used methods describe the NaHy behaviour in aqueous salt solutions by different ways. When we sort the  ${}^{app}D_{IT}^0$  according to increasing values, the order is as follows:  $MgSO_4 < Na_2SO_4 < LiCl < NaSCN$

$< \text{NaCl} < (\text{NH}_4)_2\text{SO}_4 < \text{NH}_4\text{SCN}$ . It follows that on the left side there are the salts with kosmotropic cation and anion ( $\text{K}_\text{C}\text{K}_\text{A}$ ) followed by salts containing  $\text{K}_\text{C}\text{CH}_\text{A}$  and  $\text{CH}_\text{C}\text{K}_\text{A}$ , and on the right side by salts with chaotropic cation and anion ( $\text{CH}_\text{C}\text{CH}_\text{A}$ ). However, the viscosity values behave differently, as already discussed above. Surprisingly, the data from diffusion measurements are in reasonably good agreement (opposite order) with reduced viscosity values recorded for water with dissolved salts, where NaHy was absent.

**Table 3.** Behaviour of NaHy in salt solutions observed by measurements of apparent tracer diffusion coefficients  ${}^{\text{app}}D_{\text{IT}}^0$  and reduced viscosity  $\eta_{\text{red}}$  (NaHy, Mw = 124 kDa, ionic strength 0.1 mol L<sup>-1</sup>) at 25 °C. Arrows indicate upward and downward curvature of viscosity dependences at lowest concentrations Parameter.

Salts Behaviour							
${}^{\text{app}}D_{\text{IT}}^0 \times 10^{-9} \text{ (m}^2\cdot\text{s}^{-1}\text{)}$	MgSO <sub>4</sub> KK	Na <sub>2</sub> SO <sub>4</sub> KK	LiCl KCH	NaSCN KCH	NaCl KCH	(NH <sub>4</sub> ) <sub>2</sub> SO <sub>4</sub> CHK	NH <sub>4</sub> SCN CHCH
$\eta_{\text{red water}} \text{ (L}\cdot\text{g}^{-1}\text{)}$	NH <sub>4</sub> SCN CHCH	(NH <sub>4</sub> ) <sub>2</sub> SO <sub>4</sub> CHK	NaSCN KCH	NaCl KCH	Na <sub>2</sub> SO <sub>4</sub> KK	LiCl KCH	MgSO <sub>4</sub> KK
$\eta_{\text{red NaHy at 0.1 g L}^{-1}} \text{ (L}\cdot\text{g}^{-1}\text{)}$	NaCl ↓ KCH	NH <sub>4</sub> SCN ↓ CHCH	(NH <sub>4</sub> ) <sub>2</sub> SO <sub>4</sub> ↓ CHK	LiCl ↑ KCH	Na <sub>2</sub> SO <sub>4</sub> ↑ KK	MgSO <sub>4</sub> ↑ KK	NaSCN ↑ KCH
$\eta_{\text{red NaHy at 1.5 g L}^{-1}} \text{ (L}\cdot\text{g}^{-1}\text{)}$	MgSO <sub>4</sub> KK	NaCl KCH	NH <sub>4</sub> SCN CHCH	LiCl KCH	NaSCN KCH	(NH <sub>4</sub> ) <sub>2</sub> SO <sub>4</sub> CHK	Na <sub>2</sub> SO <sub>4</sub> KK

### 3. Materials and Methods

#### 3.1. Materials

Sodium hyaluronate (NaHy), Mw = 1.8–2.1 MDa and Mw = 124 kDa were a kind gift of Contipro Ltd., (Dolní Dobrouč, Czech Republic). Sodium sulfate (Na<sub>2</sub>SO<sub>4</sub>), ammonium sulfate ((NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub>), sodium thiocyanate (NaSCN), ammonium thiocyanate (NH<sub>4</sub>SCN), sodium chloride (NaCl), lithium chloride (LiCl) and magnesium sulfate (MgSO<sub>4</sub>) were purchased from Sigma-Aldrich. All salts used were received at a purity higher than 97.5% and used as delivered. The solutions for the diffusion measurements were prepared in calibrated volumetric flasks using also Milli-Q water (from A10 Millipore) and were freshly prepared.

#### 3.2. Sample Preparation for Viscosity Measuring

For the viscosity measurements, the hyaluronan solution was prepared in concentration of 1.5 g L<sup>-1</sup> by dissolving NaHy powder in prepared salt solutions (ionic strength of 0.1 mol L<sup>-1</sup>) under continuous stirring, followed by 24-h dissolving at 50 °C. This concentration of NaHy was then diluted with respective aqueous salt solution (MgSO<sub>4</sub>, Na<sub>2</sub>SO<sub>4</sub>, (NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub>, NaSCN, NH<sub>4</sub>SCN, NaCl, LiCl) to obtain NaHy solutions with concentrations 1.0, 0.7; 0.5; 0.25 and 0.1 g L<sup>-1</sup>.

Viscosity measurements were performed using an automated viscometer SI Viscoclock (Schott Instruments, Karlsbad, Germany) equipped with Ubbelohde capillary viscometers at 25.0 ± 0.1 °C. The mean flow time of NaHy solutions through the capillary was calculated from five repeatable measurements. The relative  $\eta_{\text{rel}}$ , specific  $\eta_{\text{sp}}$  and reduced  $\eta_{\text{red}}$  viscosities of NaHy samples were subsequently calculated. The dependences between the reduced viscosity and concentration according to Huggins were then plotted and compared.

#### 3.3. Measurements of Diffusion Coefficients Using Taylor Technique

##### 3.3.1. Brief Description about Some Concepts on Diffusion

In binary NaHy<sup>+</sup> H<sub>2</sub>O solutions, the Na<sup>+</sup> and Hy<sup>-</sup> ions are required by electroneutrality to diffuse at the same speed. As a result, mutual diffusion of the electrolyte is described by Fick's law [35,36] with a single binary diffusion coefficient  $D$ , which is a weighted average of the diffusion coefficients of the ionic species.

$$J(\text{NaHy}) = -D\nabla C \quad (1)$$

From Nernst's equation, the limiting diffusion coefficient of a sodium hyaluronate (NaHy) in terms of the diffusion coefficients of the  $\text{Na}^+$  and the hyaluronate anions in units of sodium hyaluronate  $\text{Hy}^-$  ions is:

$$D^0 = \frac{2D_{\text{Na}^+}^0 D_{\text{HY}^-}^0}{D_{\text{Na}^+}^0 + D_{\text{HY}^-}^0} \quad (2)$$

However, a higher value would be expected for the tracer diffusion coefficient,  $D^0$ , compared to what would be predicted, having in mind that  $D_{\text{HY}^-}^0$  is not the limiting diffusion of polymeric HyA-anions.

The mutual diffusion of NaHy in solutions of a supporting electrolyte, such as aqueous  $\text{Na}_2\text{SO}_4$ , differs qualitatively from its diffusion in pure water. For example, the  $\text{Na}^+$  and  $\text{SO}_4^{2-}$  ions are not required to diffuse at the same speed. The diffusion of the electrolytes is coupled by the electric field (diffusion potential) generated by concentration gradients of ions with different mobilities. Diffusion in ternary NaHy(1) + salt(2) +  $\text{H}_2\text{O}$  solutions is, therefore, described by the coupled Fick equations [37,38].

$$J_1(\text{NaHy}) = -D_{11}\nabla C_1 - D_{12}\nabla C_2 \quad (3)$$

$$J_2(\text{salt}) = -D_{21}\nabla C_1 - D_{22}\nabla C_2 \quad (4)$$

$J_1$ ,  $J_2$ , and  $C_1$ ,  $C_2$  are, respectively, the molar fluxes and the gradients in the concentrations of NaHy (solute 1) and salt (solute 2).  $D_{11}$ ,  $D_{12}$ ,  $D_{21}$  and  $D_{22}$  are the ternary mutual diffusion coefficients. The main diffusion coefficients,  $D_{11}$  and  $D_{22}$ , give the flux of each solute (NaHy and salt, respectively) produced by its own concentration gradient. Cross-diffusion coefficients  $D_{12}$  and  $D_{21}$  are included for the flux of NaHy caused by the salt concentration gradient ( $C_2$ ) and the flux of salt caused by the NaHy concentration gradient ( $\nabla C_1$ ).

In a particular case, such as  $C_1/C_2 \rightarrow 0$  (corresponding to a large molar excess of salt relative to NaHy), the limiting value of the main coefficient  $D_{11}$ , of the NaHy component changes from the Nernst value in pure water (Equation (2)) to the tracer diffusion coefficient value,  $D_{\text{HY}^-}^0$ , of the  $\text{Hy}^-$  ion in aqueous salt solution. Also, in the limit  $C_1/C_2 \rightarrow 0$ , the cross-coefficient  $D_{12}$  drops to zero because a salt (2) concentration gradient is unable to drive a coupled flow of NaHy (1) in a  $\text{Hy}^-$  free solution. The cross-coefficient  $D_{21}$ , however, is not necessarily zero in the limit  $C_1/C_2 \rightarrow 0$  and, in fact, it can be quite large, especially for mixed electrolyte solutes.

Based on these considerations, the tracer diffusion of NaHy in supporting salt solutions is described by the equations:

$$J_1(\text{NaHy}) = -D_{11}\nabla C_1 \quad (5)$$

$$J_2(\text{salt}) = -D_{21}\nabla C_1 - D_{22}\nabla C_2 \quad (6)$$

Because  $D_{21}$  is not zero, a concentration gradient in the NaHy tracer will drive a significant coupled flow of NaCl in the carrier solution, producing ternary Taylor peaks (two overlapping Gaussian profiles).

### 3.3.2. The Taylor Technique: Binary Diffusion

The theory of the Taylor dispersion technique is well described in the literature [35,37–39] and consequently the authors only point out some relevant points concerning such a method on the experimental determination of binary, ternary and tracer diffusion coefficients, respectively.

Dispersion methods for diffusion measurements are based on the dispersion of small amounts of solution injected into laminar carrier streams of solvent or solution of different composition flowing through a long capillary tube. The length of the Teflon dispersion tube used in the present study was measured directly by stretching the tube in a large hall and

using two high quality theodolites and appropriate mirrors to accurately focus on the tube ends. This technique gave a tube length of  $3.2799 (\pm 0.0001) \times 10^3$  cm, in agreement with less-precise check measurements using a good-quality measuring tape. The radius of the tube,  $0.05570 (\pm 0.00003)$  cm, was calculated from the tube volume obtained by accurately weighing (resolution 0.1 mg) the tube when empty and when filled with distilled water of known density.

At the start of each run, a 6-port Teflon injection valve (Rheodyne, model 5020, Merck KGaA, Darmstadt, Germany) was used to introduce  $0.063 \text{ cm}^3$  of solution into the laminar carrier stream of slightly different composition. A flow rate of  $0.17 \text{ cm}^3 \text{ min}^{-1}$  was maintained by a metering pump (Gilson model Minipuls 3, Middleton, WI, USA) to give retention times of about  $8 \times 10^3$  s. The dispersion tube and the injection valve were kept at  $25 \text{ }^\circ\text{C}$  ( $\pm 0.01 \text{ }^\circ\text{C}$ ) in an air thermostat.

Dispersion of the injected samples was monitored using a differential refractometer (Waters model 2410) at the outlet of the dispersion tube. Detector voltages,  $V(t)$ , were measured at accurately timed 5 s intervals with a digital voltmeter (Agilent 34401 A, Santa Clara, CA, USA) with an IEEE-488 interface. Binary diffusion coefficients were evaluated by fitting the dispersion equation:

$$V(t) = V_0 + V_1 t + V_{\max} (t/t_R)^{1/2} \exp[-12D(t - t_R)^2/r^2 t] \quad (7)$$

to the detector voltages. The additional fitting parameters were the mean sample retention time  $t_R$ , peak height  $V_{\max}$ , baseline voltage  $V_0$ , and baseline slope  $V_1$ .

### 3.3.3. The Taylor Technique: Ternary Diffusion

The NaHy/salt system should be considered a ternary system, and we are actually measuring the tracer diffusion coefficients  $D_{11}^0$  but not  $D_{12}^0$ ,  $D_{21}^0$  and  $D_{22}^0$ . For ternary Taylor experiments, samples of solutions of composition  $\bar{C}_1 + \Delta C_1$ ,  $\bar{C}_2 + \Delta C_2$  are injected into laminar carrier streams of composition  $\bar{C}_1$ ,  $\bar{C}_2$ . The injected solutes spread out as they flow through a long capillary tube. A high-precision differential refractive index detector at the tube outlet monitor the broadened distributions of the dispersed solutes.

At time  $t$  after injection, the solute concentrations at the detector are [40]:

$$C_1(t) = \bar{C}_1 + \frac{2}{r^3 u} \sqrt{\frac{3}{t\pi^3}} \left[ A_{11} \sqrt{D_1} e^{-12D_1(t-t_R)^2/r^2 t} + A_{12} \sqrt{D_2} e^{-12D_1(t-t_R)^2/r^2 t} \right] \quad (8)$$

$$C_2(t) = \bar{C}_2 + \frac{2}{r^3 u} \sqrt{\frac{3}{t\pi^3}} \left[ A_{21} \sqrt{D_1} e^{-12D_1(t-t_R)^2/r^2 t} + A_{22} \sqrt{D_2} e^{-12D_1(t-t_R)^2/r^2 t} \right] \quad (9)$$

in which  $D_1$  and  $D_2$  are the eigenvalues of the matrix of the ternary  $D_{ik}$  diffusion coefficients. The detailed description of this treatment as well as the definition all parameters can be found in the literature [40].

### 3.3.4. Tracer and Apparent Tracer Diffusion

A special case of ternary diffusion arises when one of the solutes is present in trace amounts [9–11]. In the limit  $C_1/C_2 \rightarrow 0$ , for example,  $D_{11}$  is the tracer diffusion coefficient of solute 1 and  $D_{22}$  is the binary diffusion coefficient of solute 2 in the pure solvent. As noted in Section 3.3.1,  $D_{12}$  vanishes but  $D_{21}$  is not necessarily equal to zero.

The tracer diffusion of solute 1 in solutions of solute 2 is measured by injecting small volumes of solution containing both solutes 1 and 2 into carrier solutions of pure solute 2. Strong dilution of solute 1 with the carrier solution ensures its tracer diffusion. Under these conditions, because  $D_{12} = 0$ ,  $\bar{C}_1 = 0$ ,  $D_1 = D_{11}$  (the tracer diffusion coefficient of solute 1) and  $D_2 = D_{22}$  (the binary diffusion coefficient of solute 2), the general expressions for ternary concentrations profiles (Equations (8) and (9)) simplify to:

$$C_1(t) = \frac{2\Delta V \Delta C_1}{r^3 u} \sqrt{\frac{3D_{11}}{\pi^3 t}} e^{-12D_{11}(t-t_R)^2/(r^2 t)} \quad (10)$$

$$C_2(t) = \bar{C}_2 + \frac{2\Delta V}{r^3 u} \sqrt{\frac{3}{\pi^3 t}} \left[ \frac{D_{21}\Delta C_1}{(D_{11}-D_{22})} \sqrt{D_{11}} e^{-12D_{11} \frac{(t-t_R)^2}{r^2 t}} + \frac{(D_{11}-D_{22})\Delta C_2 - D_{21}\Delta C_1}{(D_{11}-D_{22})} \sqrt{D_{22}} e^{-12D_{22} \frac{(t-t_R)^2}{r^2 t}} \right] \quad (11)$$

Due to the coupled diffusion of solute 2 caused by the concentration gradient in solute 1, tracer dispersion profiles for solute 1 generally resemble two overlapping Gaussian peaks of variance  $r^2 t_R / (48D_{11})$  and  $r^2 t_R / (48D_{22})$ .

In this work, however, we considered as an approach, that for three-component solution, water (0) + NaHy(1) + salt(2), the values of tracer diffusion coefficient for the NaHy,  $D_1$ , can also be estimated by assuming there are no coupled diffusion, thus, treating the NaHy tracer Taylor peaks as simple binary ones and described by a single “pseudo-binary” tracer diffusion coefficient. In this case, we may perform a Taylor experiment for the tracer diffusion of solute 1 in which the tracer diffusion of NaHy (1) in aqueous salt (2) solutions is measured by injecting a solution of composition  $C_1 = \Delta C_1$ ,  $\bar{C}_2 = C_2$  into a carrier solution of composition  $C_1 = 0$ ,  $\bar{C}_2 = C_2$ . In this case, Equations (12) and (13)

$$C_1(t) = \frac{2\Delta V \Delta C_1}{r^3 u} \sqrt{\frac{3D_{11}}{\pi^3 t}} e^{-12D_{11} \frac{(t-t_R)^2}{r^2 t}} \quad (12)$$

$$C_2(t) = \bar{C}_2 + \frac{2\Delta V}{r^3 u} \sqrt{\frac{3}{\pi^3 t}} \left[ \frac{D_{21}\Delta C_1}{(D_{11}-D_{22})} \sqrt{D_{11}} e^{-12D_{11} \frac{(t-t_R)^2}{r^2 t}} + \frac{(D_{11}-D_{22})\Delta C_2 - D_{21}\Delta C_1}{(D_{11}-D_{22})} \sqrt{D_{22}} e^{-12D_{22} \frac{(t-t_R)^2}{r^2 t}} \right] \quad (13)$$

for the resulting concentration profiles  $C_1(t)$  and  $C_2(t)$  give

$$S(t) = \bar{S} + \frac{2\Delta V \Delta C_1 R_1}{r^3 u} \sqrt{\frac{3}{\pi^3 t}} \left[ \left( 1 + \frac{R_2}{R_1} \frac{D_{21}}{D_{11} - D_{22}} \right) \sqrt{D_{11}} e^{-12D_{11} \frac{(t-t_R)^2}{r^2 t}} - \frac{R_2}{R_1} \frac{D_{21}}{D_{11} - D_{22}} \sqrt{D_{22}} e^{-12D_{22} \frac{(t-t_R)^2}{r^2 t}} \right] \quad (14)$$

indicating the detector signal is the sum of overlapping Gaussians for diffusion coefficients  $D_{11}$  and  $D_{22}$  with relative weights  $\{1 + (R_2/R_1)D_{21}/(D_{11}-D_{22})\}$  and  $\{-(R_2/R_1)D_{21}/(D_{11}-D_{22})\}$ , respectively. Accordingly, the apparent diffusion coefficient obtained by treating the ternary tracer Taylor peak as a binary peak is:

$${}^{\text{app}}D_{1\text{Tracer}} = \left( 1 + \frac{R_2}{R_1} \frac{D_{21}}{D_{11} - D_{22}} \right) D_{11} - \left( \frac{R_2}{R_1} \frac{D_{21}}{D_{11} - D_{22}} \right) D_{22} \quad (15)$$

Equation (15) can be significantly simplified to:

$${}^{\text{app}}D_{1\text{Tracer}} = D_{11} + \frac{R_2}{R_1} D_{21} \quad (16)$$

to obtain an apparent tracer diffusion coefficient,  ${}^{\text{app}}D_{1\text{Tracer}}$ , for solute 1.

This pseudobinary treatment ignores the fact that tracer ionic diffusion in a supporting electrolyte is a multicomponent process involving coupled diffusion of the supporting electrolyte and, consequently, does not allow accurate prediction of tracer diffusion coefficients of NaHy. However, it is a useful approach, permitting us to provide qualitative information about the effect of the proposed salts on diffusion of NaHy, overcoming the great difficulties revealed in the measurement of diffusion coefficients of these systems, mainly motivated by the presence of fluids of very high viscosity.

Support for this is given by other studies [41], showing in these particular cases that the apparent tracer diffusion coefficients of these resorciararenes decrease as the concentration of the NaCl in the supporting electrolyte increases, approaching the true tracer diffusion coefficients obtained from experimental ternary Taylor dispersion profiles.

#### 4. Conclusions

Based on these measurements of diffusion coefficients of systems containing sodium hyaluronate and electrolytes in aqueous solutions, assuming that in the present experimental

conditions this system is pseudobinary, we conclude that the diffusion of this polysaccharide in aqueous solutions is strongly affected by the presence of the electrolytes. The behaviour of diffusion of NaHy in aqueous solutions changes in the presence of the salts as a result of the salting-in or salting-out effect. The salting-out effect is more favourable at high salt concentrations and when using samples of NaHy of lower molar mass. The structural differences for the forms of NaHy in solutions containing different electrolytes (extended and contracted structures, respectively) can be responsible for these phenomena.

Diffusion coefficients measured for aqueous solutions of systems containing sodium hyaluronate and salts, provide transport data necessary to model the diffusion in pharmaceutical and engineering applications.

Changes in viscosity reflect polymer interactions with the respective salt in solution, which result in bigger or smaller shrinkage of the NaHy coil. In aqueous solutions, the salts dissociate, and cations/anions interact with functional groups present in NaHy chain dependent of their position in the Hofmeister series and polymer concentration (at given ionic strength). At the lowest-used polymer concentrations, the cations and anions influence NaHy viscosity through changing the structure of water in terms of “structure making” or “structure breaking” effects.

**Author Contributions:** Conceptualization, A.M. (Aleš Mráček), A.C.F.R., A.J.M.V.; methodology, L.M., A.M. (Aleš Mráček), V.K., A.C.F.R., M.A.E. and A.J.M.V.; validation, A.M. (Aleš Mráček), A.C.F.R. and L.M.; investigation, E.F.G.A., A.C.F.R., L.M.P.V., L.M., A.M. (Aleš Mráček), V.K., A.M. (Antonín Minařík), M.M.R.; resources, A.M. (Aleš Mráček) and A.C.F.R.; Data Curation, A.M., V.K., A.M. (Aleš Mráček), M.M.R., A.J.M.V. and A.C.F.R.; Writing—Original Draft Preparation, A.C.F.R., A.J.M.V., M.A.E. and A.M. (Aleš Mráček); Writing—Review & Editing, A.C.F.R., A.J.M.V., M.A.E. and A.M. (Aleš Mráček); Visualization, A.C.F.R., A.J.M.V., M.A.E. and A.M. (Aleš Mráček); Supervision, A.M. (Aleš Mráček) and A.C.F.R.; Project Administration, A.M. (Aleš Mráček) and A.C.F.R.; Funding Acquisition, A.M. (Aleš Mráček), A.J.M.V. and A.C.F.R. All authors have read and agreed to the published version of the manuscript.

**Funding:** We are thankful to Mr. António M.C. Ferreira for the technical support for diffusion technique maintenance. This research was funded by Fundação para a Ciência e a Tecnologia (FCT) through COMPETE Programme (Operational Programme for Competitiveness), grant number UIDB/QUI/00313/2020 and by the Ministry of Education, Youth and Sports of the Czech Republic DKRVO, grant number RP/CPS/2020/003.

**Institutional Review Board Statement:** Not applicable.

**Informed Consent Statement:** Not applicable.

**Data Availability Statement:** Data is contained within the article.

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Meyer, K.; Palmer, J. The polysaccharide of the vitreous humor. *J. Biol. Chem.* **1934**, *107*, 629–640. [[CrossRef](#)]
2. *Chemistry and Biology of Hyaluronan*; Garg, H.; Hales, C. (Eds.) Elsevier Ltd.: Amsterdam, The Netherlands, 2004; ISBN 9780080443829.
3. McDonald, J.N.; Levick, J.R. Effect of intra-articular hyaluronan on pressure-flow relation across synovium in anaesthetized rabbits. *J. Physiol.* **1995**, *485*, 179–193. [[CrossRef](#)]
4. Coleman, P.J.; Scott, D.; Mason, R.M.; Levick, J.R. Characterization of the effect of high molecular weight hyaluronan on trans-synovial flow in rabbit knees. *J. Physiol.* **1999**, *514*, 265–282. [[CrossRef](#)] [[PubMed](#)]
5. Choi, J.H.; Kim, J.S.; Kim, W.K.; Lee, W.; Kim, N.; Song, C.U.; Jung, J.J.; Song, J.E.; Khang, G. Evaluation of Hyaluronic Acid/Agarose Hydrogel for Cartilage Tissue Engineering Biomaterial. *Macromol. Res.* **2020**, *28*, 979–985. [[CrossRef](#)]
6. Huynh, A.; Priefer, R. Hyaluronic acid applications in ophthalmology, rheumatology, and dermatology. *Carbohydr. Res.* **2020**, *489*, 107950. [[CrossRef](#)]
7. Azevedo, E.F.G.; Azevedo, M.L.G.; Ribeiro, A.C.F.; Mráček, A.; Grundělová, L.; Minařík, A. Hyaluronic acid transport properties and its medical applications in voice disorders. In *Innovations in Physical Chemistry: Monograph Serie, Engineering Technology and Industrial Chemistry with Applications*; Hagui, R., Torrens, F., Eds.; Apple Academic Press: Palm Bay, FL, USA, 2018; ISBN 9781771886376.
8. Lavrador, P.; Esteves, M.R.; Gaspar, V.M.; Mano, J.F. Stimuli-Responsive Nanocomposite Hydrogels for Biomedical Applications. *Adv. Funct. Mater.* **2020**, *2020*, 2005941. [[CrossRef](#)]

9. Sionkowska, A.; Gadomska, M.; Musiał, K.; Piątek, J. Hyaluronic Acid as a Component of Natural Polymer Blends for Biomedical Applications: A Review. *Molecules* **2020**, *25*, 4035. [[CrossRef](#)]
10. Zhong, W.; Pang, L.; Feng, H.; Dong, H.; Wang, S.; Cong, H.; Shen, Y.; Bing, Y. Recent advantage of hyaluronic acid for anti-cancer application: A review of “3S” transition approach. *Carbohydr. Polym.* **2020**, *238*, 116204. [[CrossRef](#)] [[PubMed](#)]
11. Bayer, I.S. Hyaluronic Acid and Controlled Release: A Review. *Molecules* **2020**, *25*, 2649. [[CrossRef](#)]
12. Vasvani, S.; Kulkarni, P.; Rawtani, D. Hyaluronic acid: A review on its biology, aspects of drug delivery, route of administrations and a special emphasis on its approved marketed products and recent clinical studies. *Int. J. Biol. Macromol.* **2020**, *151*, 1012–1029. [[CrossRef](#)]
13. Später, T.; Mariyanats, A.O.; Syachina, M.A.; Mironov, A.V.; Savelyev, A.G.; Sochilina, A.V.; Menger, M.D.; Vishnyakova, P.A.; Kananykhina, E.Y.; Fatkhudinov, T.K.; et al. In Vitro and in Vivo Analysis of Adhesive, Anti-Inflammatory, and Proangiogenic Properties of Novel 3D Printed Hyaluronic Acid Glycidyl Methacrylate Hydrogel Scaffolds for Tissue Engineering. *ACS Biomater. Sci. Eng.* **2020**, *6*, 5744–5757. [[CrossRef](#)] [[PubMed](#)]
14. Maiz-Fernández, S.; Pérez-Álvarez, L.; Ruiz-Rubio, L.; Vilas-Vilela, J.L.; Lanceros-Mendez, S. Polysaccharide-Based In Situ Self-Healing Hydrogels for Tissue Engineering Applications. *Polymers* **2020**, *12*, 2261. [[CrossRef](#)] [[PubMed](#)]
15. Sionkowska, A.; Adamiak, K.; Musiał, K.; Gadomska, M. Collagen Based Materials in Cosmetic Applications: A Review. *Materials* **2020**, *13*, 4217. [[CrossRef](#)]
16. Bhattacharya, S.; Shunmugam, R. Polymer based gels and their applications in remediation of dyes from textile effluents. *J. Macromol. Sci. Part. A* **2020**, *57*, 906–926. [[CrossRef](#)]
17. Veríssimo, L.M.P.; Valada, T.I.C.; Sobral, A.J.F.N.; Azevedo, E.E.F.G.; Azevedo, M.L.G.; Ribeiro, A.C.F. Mutual diffusion of sodium hyaluronate in aqueous solutions. *J. Chem. Thermodyn.* **2014**, *71*, 14–18. [[CrossRef](#)]
18. Mráček, A.; Gřundělová, L.; Minařík, A.; Veríssimo, L.; Barros, M.; Ribeiro, A. Characterization at 25 °C of Sodium Hyaluronate in Aqueous Solutions Obtained by Transport Techniques. *Molecules* **2015**, *20*, 5812–5824. [[CrossRef](#)]
19. Wik, K.-O.; Comper, W.D. Hyaluronate diffusion in semidilute solutions. *Biopolymers* **1982**, *21*, 583–599. [[CrossRef](#)]
20. Musilová, L.; Kašpárková, V.; Mráček, A.; Minařík, A.; Minařík, M. The behaviour of hyaluronan solutions in the presence of Hofmeister ions: A light scattering, viscometry and surface tension study. *Carbohydr. Polym.* **2019**, *212*, 395–402. [[CrossRef](#)] [[PubMed](#)]
21. Vlachy, N.; Jagoda-Cwiklik, B.; Vácha, R.; Touraud, D.; Jungwirth, P.; Kunz, W. Hofmeister series and specific interactions of charged headgroups with aqueous ions. *Adv. Colloid Interface Sci.* **2009**, *146*, 42–47. [[CrossRef](#)]
22. Zhang, Y.; Cremer, P. Interactions between macromolecules and ions: The Hofmeister series. *Curr. Opin. Chem. Biol.* **2006**, *10*, 658–663. [[CrossRef](#)]
23. Leontidis, E. Investigations of the Hofmeister series and other specific ion effects using lipid model systems. *Adv. Colloid Interface Sci.* **2017**, *243*, 8–22. [[CrossRef](#)]
24. Budroni, M.A.; Rossi, F.; Wodlei, F.; Marchettini, N.; Lo Nostro, P.; Rustici, M. Hofmeister effect in self-organised chemical systems. *J. Phys. Chem. C* **2020**. [[CrossRef](#)]
25. Sarri, F.; Tatini, D.; Tanini, D.; Simonelli, M.; Ambrosi, M.; Ninham, B.W.; Capperucci, A.; Dei, L.; Lo Nostro, P. Specific ion effects in non-aqueous solvents: The case of glycerol carbonate. *J. Mol. Liq.* **2018**, *266*, 711–717. [[CrossRef](#)]
26. Mazzini, V.; Liu, G.; Craig, V.S.J. Probing the Hofmeister series beyond water: Specific-ion effects in non-aqueous solvents. *J. Chem. Phys.* **2018**, *148*, 222805. [[CrossRef](#)]
27. Mráček, A.; Varhaníková, J.; Lehocký, M.; Gřundělová, L.; Pokopcová, A.; Velebný, V. The Influence of Hofmeister Series Ions on Hyaluronan Swelling and Viscosity. *Molecules* **2008**, *13*, 1025–1034. [[CrossRef](#)]
28. Mráček, A. The Measurement of Polymer Swelling Processes by an Interferometric Method and Evaluation of Diffusion Coefficients. *Int. J. Mol. Sci.* **2010**, *11*, 532–543. [[CrossRef](#)]
29. Mráček, A.; Benešová, K.; Minařík, A.; Urban, P.; Lapčík, L. The diffusion process of sodium hyaluronate (Na-Ha) and Na-Ha-n-alkyl derivatives films swelling. *J. Biomed. Mater. Res. Part. A* **2007**, *83A*, 184–190. [[CrossRef](#)]
30. Kunz, W. Specific ion effects in colloidal and biological systems. *Curr. Opin. Colloid Interface Sci.* **2010**, *15*, 34–39. [[CrossRef](#)]
31. Bastos-González, D.; Pérez-Fuentes, L.; Drummond, C.; Faraudo, J. Ions at interfaces: The central role of hydration and hydrophobicity. *Curr. Opin. Colloid Interface Sci.* **2016**, *23*, 19–28. [[CrossRef](#)]
32. Walstra, P. *Physical Chemistry of Foods*; CRC Press: Boca Raton, FL, USA, 2002; ISBN 9780203910436.
33. Cowman, M.K.; Matsuoka, S. Experimental approaches to hyaluronan structure. *Carbohydr. Res.* **2005**, *340*, 791–809. [[CrossRef](#)] [[PubMed](#)]
34. Applebey, M.P. CXXI—The viscosity of salt solutions. *J. Chem. Soc. Trans.* **1910**, *97*, 2000–2025. [[CrossRef](#)]
35. Tyrrell, H.J.V.; Harris, K.R. *Diffusion in Liquids: A Theoretical and Experimental Study*; Butterworth: London, UK, 1984; ISBN 978040-8175913.
36. Harned, H.; Owen, B. *The Physical Chemistry of Electrolytic Solutions*, 3rd ed.; Reinholds: New York, NY, USA, 1964; ISBN 978-027-8917293.
37. Barthel, J.; Gores, H.J.; Lohr, C.M.; Seidl, J.J. Taylor dispersion measurements at low electrolyte concentrations. I. Tetraalkylammonium perchlorate aqueous solutions. *J. Solut. Chem.* **1996**, *25*, 921–935. [[CrossRef](#)]
38. Callendar, R.; Leaist, D.G. Diffusion Coefficients for Binary, Ternary, and Polydisperse Solutions from Peak-Width Analysis of Taylor Dispersion Profiles. *J. Solut. Chem.* **2006**, *35*, 353–379. [[CrossRef](#)]

39. Price, W.E. Theory of the Taylor dispersion technique for three-component-system diffusion measurements. *J. Chem. Soc. Faraday Trans. Phys. Chem. Condens. Phases* **1988**, *84*, 2431. [[CrossRef](#)]
40. Deng, Z.; Leaist, D.G. Ternary mutual diffusion coefficients of  $\text{MgCl}_2 + \text{MgSO}_4 + \text{H}_2\text{O}$  and  $\text{Na}_2\text{SO}_4 + \text{MgSO}_4 + \text{H}_2\text{O}$  from Taylor dispersion profiles. *Can. J. Chem.* **1991**, *69*, 1548–1553. [[CrossRef](#)]
41. Galindres, D.M.; Ribeiro, A.C.F.; Esteso, M.A.; Vargas, E.F.; Leaist, D.G.; Rodrigo, M.M. The effects of sodium chloride on the diffusion of sulfonated resorcinarenes in aqueous solutions. *Fluid Phase Equilib.* **2020**, *518*, 112629. [[CrossRef](#)]